

Review Article

A Review of the Potential Applications of Composites from Agricultural Waste

Mbatha Abednigo Jabu¹, AA Alugongo², NZ Nkomo³

^{1,2,3}Vaal University of Technology, Department of Mechanical Engineering, Industrial Engineering and Operation Management Private Bag X021, Vanderbijlpark, South Africa.

¹Corresponding Author : abednigom@vut.ac.za

Received: 16 August 2024

Revised: 14 November 2024

Accepted: 19 December 2024

Published: 31 January 2025

Abstract - The disposal of agricultural waste is a challenge in our environment; it keeps increasing with the increase in population and production. The automotive industry has used agricultural waste, such as macadamia shells, to fabricate automobile door panels. The use of agricultural waste in the automotive industry lessens pollution and promotes sustainability in the environment. This paper reviews how effectively agricultural waste composites can be used in the automotive industry, eliminating waste in the landfill. Agricultural waste composites have a lot of potential in the automotive industry since they are recyclable and biodegradable, which makes disposing of them extremely convenient and eco-friendly. Furthermore, using agricultural waste bio-composites lowers the cost of production of automotive parts. There is still a need for further research into various agricultural waste, which has not been explored in the automotive industry and other applications.

Keywords - Automotive industry, Agricultural waste, Composites, Polymers, Bio-composite.

1. Introduction

Agricultural operations create a significant amount of waste, which frequently winds up in landfills, and according to predictions, it will rise to 9 billion by 2050 and 11 billion by 2100, respectively [1]. Effective waste management is essential in preserving a habitable ecology. Agricultural waste generation is a significant burden on the environment. The food and forestry industry activities result in large amounts of agricultural byproducts often treated as waste and sent to landfills. Technological advancements have increased agricultural output significantly. Furthermore, the rising population has necessitated increased agricultural production, which has expanded more than three times over the last 50 years [2].

All over the world, the agriculture sector generates approximately 23.7 million tons of food every day [3]. Billions of tons of agricultural waste are produced worldwide in a year [4, 5]. Current agricultural production systems have and are still undergoing significant modifications as a result of the more sustainable development models that have been driven in recent years [6]. They are different types of agricultural waste, as shown in Figure 1. However, this paper focuses on agricultural waste disposed of in landfills. Recycling agricultural waste has both positive economic and environmental advantages. Thus, the economic evaluation of bioenergy from agricultural waste has emerged as a crucial area of study [7-9].

Biopolymer-based composites are produced from agricultural waste biomass when biopolymers and biomass are combined. The term biopolymers describes a class of naturally occurring polymers produced by living things, such as proteins, polysaccharides, and nucleic acids. Agricultural waste is the term used to describe biomass produced from agricultural leftovers. This includes byproducts, including sawdust, animal manure, and leftover crop material, as shown in Figure 1 [10, 11].

Enhancing the recovery efficiency of agricultural waste is anticipated to be made easier by the updated recycling management procedures. Agricultural waste recycling has become a developing industry because of policy support and increased recycling awareness. Agricultural waste is being recycled by farmers more often than being burned or dumped in landfills [13].

In automotive industries, biopolymer-based composites manufactured from biomass derived from agricultural waste offer an environmentally responsible and sustainable alternative to conventional materials. Composites, made by combining biopolymers and agricultural waste biomass, can be used for several things, such as medical equipment, building materials, automotive parts, biofuels, packaging, and soil enhancement. These composites have improved properties over conventional materials and lower the environmental impact of agricultural waste on the environment [14].



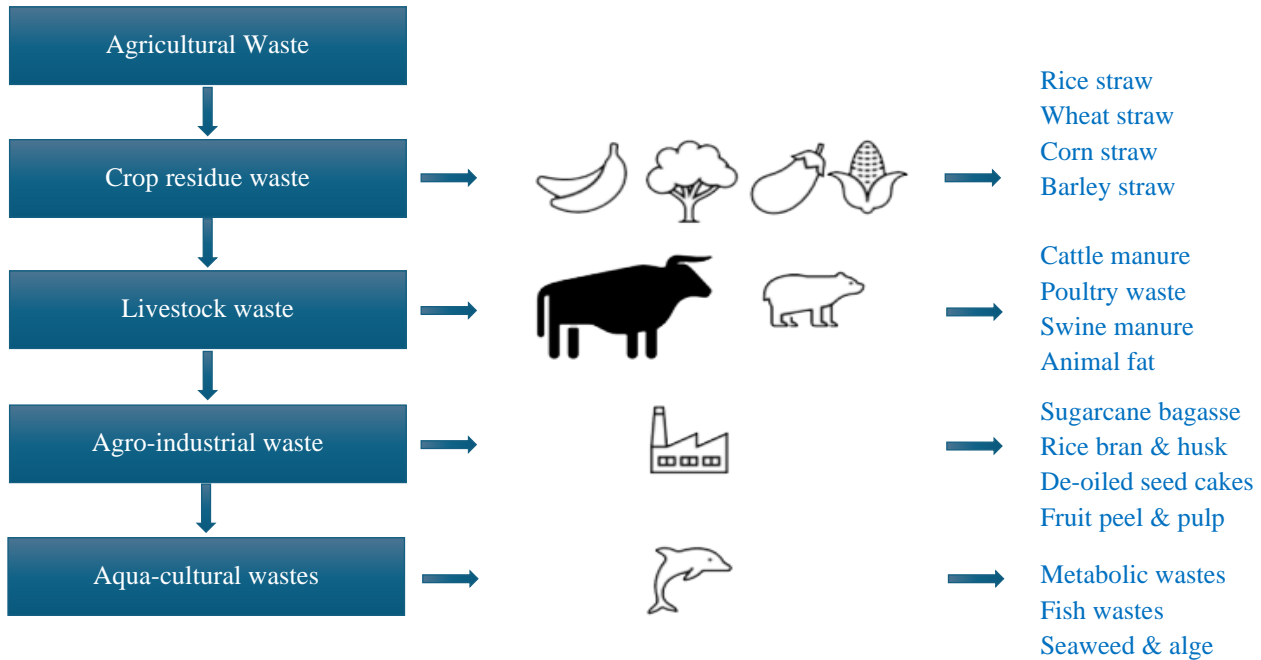


Fig. 1 Waste materials classification [12]

2. Macadamia Shells

Macadamia shells can be used for various creative product designs because they are recyclable and biodegradable [15]. The global macadamia production is around 120,000 tons in shell, equivalent to 36,000 tons in kernel form [16]. Australia's food industry generates 28,000 tons of byproduct empty macadamia shells, disposed of as waste in landfills [17]. The annual worldwide production of macadamia nuts continues to increase, and with it is the generation of waste shells, which account for 65% of the entire nut. In common with other agricultural waste, macadamia nutshells are burned as solid biomass fuel, used as garden mulch, animal bedding, cooking fuel, or thrown away entirely.



Fig. 2 Macadamia nuts [22]

It is noteworthy that macadamia nutshells differ significantly from natural wood in terms of their density and structure, although having surprisingly comparable chemical makeup [18]. The nutshell of a macadamia is brittle and hard [19]. Because of the low density of the macadamia shell, it performs better than ordinary ceramics and glass when compared based on specific strength or modulus. It is known to have roughly the same fracture toughness as comparable materials [20]. Empty shells, or macadamia leftovers, are underutilized and typically thrown in the trash. Alternatively, they are burnt and used as garden mulch, animal filler, or chicken litter [21]. Sustainable recycling solutions are vital since the disposal of macadamia nut shells has caused major issues for the nut processing sectors. Making wood polymer composites using macadamia nut shells is one potential remedy. Due to the mechanical characteristics of macadamia shells, they can be used with thermoset resins to create wood-plastic composites (WPC) [23 - 28].

The macadamia nut industry is still growing worldwide, with shells and other debris comprising around 70% of the fruit's weight [19]. Unfortunately, there is still a lot of untapped potential when using macadamia shells as byproducts [21]. Polymeric composites filled with macadamia nutshells have great promise for producing a range of structural elements, such as sandwich composites, which could be used in the infrastructure, aerospace, and automotive sectors. Additionally, macadamia shells can be treated at high temperatures in a specific low-oxygen environment to provide biochar. Biochar is used in cosmetics, industrial nanopowders, life-saving medical therapies, and carbon filters [29].

3. Coconut Shell

The hard, lignocellulosic agro-waste portion of the coconut that is not edible is called the shell. The coconut shell accounts for 15% to 20% of the coconut [30].

Table 1. Properties of coconut [39]

Aggregate impact value (%)	4.26
Los Angeles abrasion value (%)	14.88
Specific gravity	1.45
Water absorption	17.3

**Fig. 3 Coconut shell [32]**

Due to their superior thermal stability over other agricultural waste, coconut shells could make for highly intriguing filler materials in biodegradable polymer composites [31]. The coconut shell shown in Figure 3 can be crushed into particles, much like wood particles. The majority of the carbohydrates found in coconut shells include cellulose, hemicelluloses, and lignin [30]. Research on natural fibre reinforced polymer composites has been conducted extensively; however, there is very little study on polymer composites based on fillers made of coconut shell particles. Table 1 shows the physical properties of the coconut shells. The use of coconut shell particles as fine and coarse aggregates in concrete with replacement percentages ranging from 0% to 30%, or from 10% to 20% to 30%, is the subject of an experimental investigation on the M20 Concrete strength criteria. Compressive strength and tensile strength for 7, 28, and 56 days with and without coconut shell aggregates, and we've found that the concrete with a 20% coconut shell substitution shows good strength. It has been demonstrated that using coconut shells to partially replace coarse aggregate is feasible [33].

4. Rice Straw

The amount of rice produced worldwide between 2007 and 2017 increased to 756,7 million tons [34]. However, rice straws are generally not disposed of in an environmentally friendly way [35]. These rice straw wastes, which are mostly made up of cellulose, hemicellulose, and lignin, are typically not suitable for use as animal feed [36]. Rice straw's chemical composition is approximately 7.36% silica, 38.7% carbon, 2.37% potassium, 1.13% calcium, 0.53% magnesium, and water [37]. Due to the combustibility of rice straw, open-air burning is considered an accepted disposal method.

**Fig. 4 Rice straw [32]**

Disposal of rice straw through incineration causes harm to the environment [35]. There has been a lot of research into methods of recycling these byproducts into biomass [38]. Green composites are made of fibre and matrix made from renewable resources. These composite materials are referred to as partially eco-friendly if some of the constituents are not made of renewable materials [39, 40]. Rice straws, as shown in Figure 4, have many advantageous qualities, including low density and renewable nature, making them suitable for use in biocomposites [41]. Rice straw has been used in different applications, such as furniture, interior decoration and the construction of walls and ceilings [42]. Rice Straw Particles and *Furcraea foetida* Fibre Reinforced Hybrid Composite. In this work, a hybrid composite reinforced with Rice Straw Particle (RSp) and *Furcraea Foetida* (FF) fiber was created, and its mechanical and physical characteristics were examined. The test samples' density was lowered by 41.87% upon adding 15% weight percent of RSp, and their water absorption (WA) rose as fiber concentration rose. The composite with 5 weight percent and 15 weight percent RSp demonstrated maximum modulus (σ_{tm} : 3.67 GPa) and tensile strength (σ_t : 29.45 MPa), respectively. The maximum flexural strength (σ_f : 43.12 MPa) and modulus (σ_{fm} : 2.09 GPa) were reached at 15% of RSp, whereas the highest impact strength (σ_i : 101.01 J/m) was seen at 10% of RSp. The RSp reinforced composite's σ_t (40.21%) and σ_f (7.76%) were enhanced by the hybridization of FF (20wt.%) fibre reinforcement.

5. Wheat Straw

Since 2007, wheat straw production has been approximately 540 million tons annually worldwide [43]. The majority of these farming wastes are left on the ground to decompose after harvest or burnt in open fields and, cause air pollution [44, 45]. However, some small amounts of wheat straw have been utilized as bedding and nutrition for animals [46]. Another popular use of wheat straw waste is directly chopping and grinding into particles, subsequently used to create composites [47]. Wheat straws can be used to make lightweight composites.

Table 2. Properties of wheat straw [50]

Properties	Untreated	Treated
Bulk density $\rho_{\text{bulk, dried}}$ (kg m ⁻³)	100	100
Porosity (%)	0.90	0.90
Specific heat capacity C_p (J kg ⁻¹ K ⁻¹)	1735	1745
Thermal conductivity λ (W m ⁻¹ K ⁻¹)	0.061	0.059
Vapour diffusion resistance factor μ (dimensionless)	5	5
Moisture content at RH=80%	0.14	0.15

Composites with densities less than the total density contributions from all materials used to construct them are considered lightweight [48, 49]. The properties of wheat straw are shown in Table 2. The properties of wheat straw give the possibility of their use in interior panel composites in the automotive industry. Chopped wheat straw reinforcement and epoxy resin matrix, or hybrid resins varied up to 50% and 70% Damar volume fractions, were used to produce composites. The maximum flexural strength of 35.6 MPa, compression strength of 28.8MPa and tensile strength of 14.58 MPa were obtained from fabricated composites [51].

6. Corn Straw

The most common food crop farmed worldwide is corn [52]. With the United States and China controlling half of the worldwide market, it has expanded throughout numerous nations [53]. Consequently, there is also a lot of corn straw (CS) waste. The corn straw is mostly composed of cellulose, hemicellulose, and lignin. Corn straw is a plentiful and renewable biomass resource that is frequently utilized for water purification, feed and green composites [54-56]. However, corn straw recycling is important for protecting the environment and conserving resources [57]. Corn straw is an industrial raw material source with a wide range of possible uses, such as filler material [58]. The utilization of agricultural residues can successfully lower costs in the artificial panel manufacturing business, promote sustainability, and minimize air pollution generated by the combustion of corn residues [59].

The chemical composition of corn straw is shown in Table 3. Wheat straw development of transparent composites using wheat straw fibres for light-transmitting building applications was fabricated through the effective impregnation of pre-polymerized methyl methacrylate (MMA) into wheat straw (TCWS), transparent composites were accomplished [60]. The bio-based composites had excellent mechanical and light transmittance qualities because the microscopic morphology examination revealed that WSF had a strong binding performance with polymethyl methacrylate (PMMA). Tensile strength of 58.19 MPa, impact strength of 4.26 kJ/m², haze of 54.63%, light transmittance of 74.63%, and thickness of 3 mm were observed in the TCWS with 30 weight percent WSF. According to TCWS's thermal property test, the material has outstanding thermal insulation ability, with a heat conductivity of 0.07 Wm⁻¹k.

Table 3. Composition of corn before and after pretreatment (mass fraction) [64]

	Cellulose	Hemicellulose	Lignin
Untreated	37.6	25.8	17.4
With CH ₃ COOH	42.5	24.6	16.9
with NaOH	45.9	24.2	15.6

Additionally, TCWS demonstrated superior UV resistance and thermal dimensional stability. In light of this, TCWS may find use in the transparent building industry. Consequently, there may be opportunities for TCWS to be applied in the field of transparent structures. Compared to wood fiber transparent composites, the novelties of this study are in turning low-cost agricultural leftovers into high-value transparent composites with increased thermal insulation qualities for light-transmitting construction applications [60].

7. Barley Straw

Barley is a globally significant grain crop, farmed in over 44 million hectares with a yield of 141 million tons of grain [2]. Barley straw serves as a significant source of lignocellulose, which can be utilized as a reinforcement for polymeric matrices or as a raw material in various industrial processes [61, 62]. However, barley straw has the challenge of excessive moisture absorption. Nevertheless, lightweight bio-aggregates (lignocellulosic materials) like barley straws have been the subject of several studies that have attempted to improve the properties of lightweight bio-composites or eco-materials by lowering the rate at which the bio-aggregates absorb water. Physically treating barley straws, for instance [63]. Barley straw and a biobased polyethylene (BioPE) polymer matrix were used to create biobased composites. BioPE is 100% recyclable and entirely biobased. Regarding material performance, research was done on the materials' flexural characteristics. Achieving a proper distribution of reinforcement within the plastic led to elevated increases in flexural strength. An increase in flexural strength of almost 147% was obtained at 45 weight percent of reinforcement. A barley straw fibre flexural strength factor was used to determine the mean contribution of the fibres to the flexural strength, and the result was 91.4. With coupling factors ranging from 0.18 to 0.19, the intrinsic flexural strength of the barley straw fibres could be predicted using the micromechanical analysis, reaching up to about 700 MPa [64].

Table 4. Properties of barley straw [50]

Properties	Value
Bulk density $\rho_{\text{bulk, dried}}$ (kg m ⁻³)	100
Porosity (%)	0.89
Specific heat capacity C_p (J kg ⁻¹ K ⁻¹)	1645
Thermal conductivity λ (W m ⁻¹ K ⁻¹)	0.052
Vapour diffusion resistance factor μ (dimensionless)	5
Moisture content at RH=80%	0.13

8. Benefits of Agricultural Waste Materials

Synthetic composites, often made of non-renewable materials and not biodegradable, have an adverse effect on the environment when disposed of [65, 66]. The application of biomass from agricultural waste as a biopolymer-based composite shows a wide range of potential applications not only in automotive but across several industries [67-70]. Natural fillers have several advantages over conventional ones, including being less expensive, having high toughness, low density, strong specific strength qualities, and reducing tool wear [71]. Cars utilizing natural fibre composites are lighter, hence lowering their fuel consumption [72]. Natural fibre composites have advantages in the automotive industry, giving better thermal and acoustic qualities [73, 74].

9. Application of Agricultural Waste in the Automotive Industry

The automotive manufacturing industry is responsible for 60–70% of the global air pollution causes [75, 76]. Vehicles release a great deal of harmful gasses, including lead and fine particulates, hydrocarbons (HC), nitrogen oxides (NOX), and carbon monoxide (CO) [77-79]. According to projections, the current rate of car production worldwide will triple by the end of 2050 (ReF). The transportation sector will have a greater impact on climate change as a result of the increase in Carbon Dioxide (CO₂) and other hazardous equivalent gas emissions [75]. The environment is under pressure as a result of this increase in worldwide production, to the point where soil, air, and water resources are being compromised [80]. Ford used coconut shells and rubber from waste tyres to fabricate battery housing, structural guards, lightweight armrests, applique brackets and door cladding [81, 72]. Biocomposites made of renewable resources, including agricultural waste, have a lot of promise to help automobiles and developers as the environment and petroleum supplies are depleted quickly. Due to their unique qualities, biocomposites can be used to produce dashboards, headliners, seat backs, and wood trim [75, 72]. seat fillers, and other non-structural interior components.

They can also be used for thermoacoustic insulation. Audi now employs polyurethane and loose/sisal natural fibers for door trim panels, while certain of its car models use biocomposites based on cellulose for boot lid finish panels, door panels, and seatbacks [84]. Ford also uses agricultural waste to produce parts, such as cabin storage bins composed of polypropylene and wheat straw, which increase farmer revenue and decrease pollution [85].

References

- [1] S.H.A. Koop, and C.J. Van Leeuwen, "The Challenges of Water, Waste and Climate Change in Cities," *Environment, Development and Sustainability*, vol. 19, no. 2, pp. 385-418, 2017. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [2] Helen Canton, *Food and Agriculture Organization of the United Nations-FAO*, The Europa Directory of International Organizations, 23rd ed., pp. 297-305, 2021, Routledge, 2021. [[Google Scholar](#)] [[Publisher Link](#)]
- [3] Clayton Campanhola, and Shivaji Pandey, *Strategic Work of FAO for Sustainable Food and Agriculture*, Food and Agriculture Organization of the United Nations, pp. 1-28, 2017. [[Google Scholar](#)] [[Publisher Link](#)]

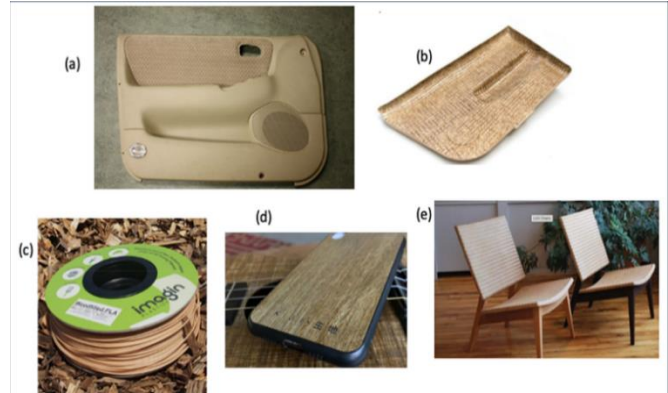


Fig. 5 Lightweight bio-composites applications [82], [83]

10. Conclusion

Agricultural waste has a lot of potential end uses, and this trend will only grow as more ecologically conscious and sustainable transportation methods are adopted. The automotive sector reduces and simplifies the disposal of agricultural waste, thereby removing potential risks from landfills. Unlike most synthetic fillers, agricultural waste is biodegradable, recyclable, and inexpensive. Sustainable biopolymer-based composites for lightweight applications made from biomass from agricultural waste are a promising field that holds great promise for solving some of the most important environmental and financial issues of our day. These composites not only offer improved mechanical qualities and biodegradability, but they also have the potential to replace conventional materials in various applications, such as home, automotive, maritime, and packaging. Utilizing agricultural waste has the potential to generate employment opportunities and reduce the cost of components in the automotive industry.

Funding Statement

This study is funded by the Vaal University of Technology.

Acknowledgement

This research work was supported by the Vaal University of Technology. The authors thank the Department of Industrial Engineering, Operation Management and Mechanical Engineering at Vaal University of Technology for facilitating this work.

- [4] Silpa Kaza et al., *What a Waste 2.0: a Global Snapshot of Solid Waste Management to 2050*, World Bank Publications, pp. 1-292, 2018. [[Google Scholar](#)] [[Publisher Link](#)]
- [5] R. Nagendran, *Agricultural Waste and Pollution*, Waste: A Handbook for Management, pp. 341-355, 2011. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [6] “*Agriculture and Food Security*,” Ethiopian Panel on Climate Change: First Assessment Report, Ethiopian Academy of Sciences, pp. 1-230, 2016. [[Google Scholar](#)] [[Publisher Link](#)]
- [7] Steve Dagnall, Jon Hill, and David Pegg, “Resource Mapping and Analysis of Farm Livestock Manures-Assessing the Opportunities for Biomass-to-Energy Schemes,” *Bioresource Technology*, vol. 71, no. 3, pp. 225-234, 2000. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [8] Delzeit Ruth, Britz Wolfgang, and Kreins Peter, *An Economic Assessment of Biogas Production and Land Use under the German Renewable Energy Source Act*, Kiel Institute for the World Economy (IfW), Kiel, pp. 1-26, 2012. [[Google Scholar](#)] [[Publisher Link](#)]
- [9] Harish Kumar Jeswani et al., “Environmental and Economic Sustainability of Poultry Litter Gasification for Electricity and Heat Generation,” *Waste Management*, vol. 95, pp. 182-191, 2019. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [10] Rafael Auras, Bruce Harte, and Susan Selke, “An Overview of Poly lactides as Packaging Materials,” *Macromolecular Bioscience*, vol. 4, no. 9, pp. 835-864, 2004. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [11] Abdus Sobhan, Kasiviswanathan Muthukumarappan, and Lin Wei, “Biosensors and Biopolymer-Based Nanocomposites for Smart Food Packaging: Challenges and Opportunities,” *Food Packaging and Shelf Life*, vol. 30, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [12] Syaifullah Muhammad et al., “Insights into Agricultural-Waste-Based Nano-Activated Carbon Fabrication and Modifications for Wastewater Treatment Application,” *Agriculture*, vol. 12, no. 10, pp. 1-20, 2022. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [13] Esher Hsu, “Cost-Benefit Analysis for Recycling of Agricultural Wastes in Taiwan,” *Waste Management*, vol. 120, pp. 424-432, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [14] T.G. Yashas Gowda et al., “Biopolymer-Based Composites: An Eco-Friendly Alternative from Agricultural Waste Biomass,” *Journal of Composites Science*, vol. 7, no. 6, pp. 1-20, 2023. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [15] Duygu Gokdai, Alev Akpınar Borazan, and Gokhan Acikbas, “Effect of Marble: Pine Cone Waste Ratios on Mechanical Properties of Polyester Matrix Composites,” *Waste and Biomass Valorization*, vol. 8, pp. 1855-1862, 2017. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [16] Fangyu Fan et al., “Preparation and Properties of Hydrochars from Macadamia Nut Shell via Hydrothermal Carbonization,” *Royal Society Open Science*, vol. 5, no. 10, pp.1-10, 2018. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [17] Jun-Seok Bae, and Shi Su, “Macadamia Nut Shell-Derived Carbon Composites for Post Combustion CO₂ Capture,” *International Journal of Greenhouse Gas Control*, vol. 19, pp. 174-182, 2013. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [18] Andrea Wechsler et al., Sustainable Furniture Panel Composites from Forestry and Food Industry By-Products in Australia,” *Conference proceedings eddBE2011 sustainable wellbeing*, Brisbane Australia, pp. 1-7, 2011. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [19] Chun-Hui Wang, Liangchi Zhang, and Yiu-Wing Mai, “Deformation and Fracture of Macadamia Nuts: Part 1: Deformation Analysis of Nut-in-Shell,” *International Journal of Fracture*, vol. 69, pp. 51-65, 1994. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [20] Kumar Rakesh, Ofosu Osei, and Anandjiwala Rajesh D, “Macadamia Nutshell Powder Filled Poly Lactic Acid Composites with Triacetin as a Plasticizer,” *Journal of Biobased Materials and Bioenergy*, vol. 7, no. 5, pp. 541-548, 2013. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [21] Ravindra Rajarao, and Veena Sahajwalla, “A Cleaner, Sustainable Approach for Synthesising High Purity Silicon Carbide and Silicon Nitride Nanopowders using Macadamia Shell Waste,” *Journal of Cleaner Production*, vol. 133, pp. 1277-1282, 2016. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [22] Paul Schuler et al., “Structure-Function Relationships in Macadamia Integrifolia Seed Coats–Fundamentals of the Hierarchical Microstructure,” *PLOS One*, vol. 9, no. 8, pp. 1-14, 2014. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [23] Faris M. AL-Oqla et al., “Natural Fiber Reinforced Conductive Polymer Composites as Functional Materials: A Review,” *Synthetic Metals*, vol. 206, pp. 42-54, 2015. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [24] Juliana S. Felix, Celia Domeño, and Cristina Nerín, “Characterization of Wood Plastic Composites made from Landfill-Derived Plastic and Sawdust: Volatile Compounds and Olfactometric Analysis,” *Waste Management*, vol. 33, no. 3, pp. 645-655, 2013. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [25] N.A.M. Aridi et al., “Investigating Morphological and Performance Deterioration of Injection-Molded Rice Husk-Polypropylene Composites due to Various Liquid Uptakes,” *International Journal of Polymer Analysis and Characterization*, vol. 21, no. 8, pp. 675-685, 2016. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [26] Uttam Kumar et al., “Cleaner Production of Iron by using Waste Macadamia Biomass as a Carbon Resource,” *Journal of Cleaner Production*, vol. 158, pp. 218-224, 2017. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [27] Chensong Dong, and Ian J. Davies, “Flexural Properties of Macadamia Nutshell Particle Reinforced Polyester Composites,” *Composites Part B: Engineering*, vol. 43, no. 7, pp. 2751-2756, 2012. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]

- [28] T. J. Kowitz et al., “Storage of Macadamia Nut-In-Shell,” *Australian Macadamia Society News Bulletin*, pp. 61-67, 1996. [[Google Scholar](#)] [[Publisher Link](#)]
- [29] Md Sefat Khan et al., “Exploring the Prospects of Macadamia Nutshells for Bio-Synthetic Polymer Composites: A Review,” *Polymers*, vol. 15, no. 19, pp. 1-15, 2023. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [30] F. P. La Mantia, M. Morreale, and Z. A. Mohd Ishak, “Processing and Mechanical Properties of Organic Filler-Polypropylene Composites,” *Journal of Applied Polymer Science*, vol. 96, no. 5, pp. 1906-1913, 2005. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [31] Fatih Mengeloglu, and Laurent M. Matuana, “Mechanical Properties of Extrusion-Foamed Rigid PVC/Wood-Flour Composites,” *Journal of Vinyl and Additive Technology*, vol. 9, no. 1, pp. 26-31, 2003. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [32] N. Sathiparan, and H. T. S. M. De Zoysa, “The Effects of Using Agricultural Waste as Partial Substitute for Sand in Cement Blocks,” *Journal of Building Engineering*, vol. 19, pp. 216-227, 2018. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [33] Parag S. Kambli, and Sandhya R. Mathapati, “Application Of Coconut Shell As Coarse Aggregate In Concrete,” *International Journal of Engineering Research and Applications*, vol. 4, no. 3, pp. 498-501, 2014. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [34] E.R. Abaide, M.V Tres, G.L. Zabot, and M.A. Mazutti, “Reasons for Processing of Rice Coproducts: Reality and Expectations,” *Biomass and Bioenergy*, vol. 120, pp. 240-256, 2019. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [35] Butchaiah Gadde ET AL., “Air Pollutant Emissions from Rice Straw Open Field Burning in India, Thailand and the Philippines,” *Environmental Pollution*, vol. 157, no. 5, pp. 1554-1558, 2009. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [36] Raveendran Sindhu, Parameswaran Binod, and Ashok Pandey, “Biological Pretreatment of Lignocellulosic Biomass—an Overview,” *Bioresource Technology*, vol. 199, pp. 76-82, 2016. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [37] Minh Ngoc Nguyen et al., “Release of Potassium Accompanying the Dissolution of Rice Straw Phytolith,” *Chemosphere*, vol. 119, pp. 371-376, 2015. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [38] J.R. Gonzalez-Lopez et al., “Small Addition Effect of Agave Biomass Ashes in Cement Mortars,” *Fuel Processing Technology*, vol. 133, pp. 35-42, 2015. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [39] Michael P.M. Dicker et al., “Green Composites: A Review of Material Attributes and Complementary Applications,” *Composites Part A: Applied Science and Manufacturing*, vol. 56, pp. 280-289, 2014. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [40] B.C. Mitra, “Environment Friendly Composite Materials: Biocomposites and Green Composites,” *Defence Science Journal*, vol. 64, no. 3, pp. 244-261, 2014. [[Google Scholar](#)] [[Publisher Link](#)]
- [41] Zakia Hussein et al., “Rice Straw and Flax Fiber Particleboards as a Product of Agricultural Waste: An Evaluation of Technical Properties,” *Applied Sciences*, vol. 9, no. 18, pp. 1-20, 2019. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [42] R.M. Mohsen et al., “Review on the Manufacture of Particleboard from Agro-Wastes using Different Adhesives,” *Egyptian Journal of Chemistry*, vol. 57, no. 3, pp. 165-176, 2014. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [43] Narendra Reddy, and Yiqi Yang, “Preparation and Characterization of Long Natural Cellulose Fibers from Wheat Straw,” *Journal of Agricultural and Food Chemistry*, vol. 55, no. 21, pp. 8570-8575, 2007. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [44] Anke Schirp et al., “Pilot-Scale Production and Material Properties of Extruded Straw-Plastic Composites based on Untreated and Fungal-Treated Wheat Straw,” *Forest Products Journal*, vol. 56, no. 10, pp. 90-96, 2006. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [45] Ayse Alemdar, and Mohini Sain, “Biocomposites from Wheat Straw Nanofibers: Morphology, Thermal and Mechanical Properties,” *Composites Science and Technology*, vol. 68, no. 2, pp. 557-565, 2008. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [46] S. Panthapulakkal, A. Zereshkian, and M. Sain, “Preparation and Characterization of Wheat Straw Fibers for Reinforcing Application in Injection Molded Thermoplastic Composites,” *Bioresource Technology*, vol. 97, no. 2, pp. 265-272, 2006. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [47] T. Hervillard, Q. Cao, and M.P.G. Laborie, “Improving Water Resistance of Wheat Straw-Based Medium Density Fiberboards Bonded with Aminoplastic and Phenolic Resins,” *Bioresources*, vol. 2, no. 2, pp. 148-156, 2007. [[Google Scholar](#)] [[Publisher Link](#)]
- [48] Shah Huda, and Yiqi Yang, “Feather Fiber Reinforced Light-Weight Composites with Good Acoustic Properties,” *Journal of Polymers and the Environment*, vol. 17, pp. 131-142, 2009. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [49] Shah Huda, and Yiqi Yang, “A Novel Approach of Manufacturing Light-Weight Composites with Polypropylene Web and Mechanically Split Cornhusk,” *Industrial Crops and Products*, vol. 30, no. 1, pp. 17-23, 2009. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [50] C.H. Koh et al., “Resources, Conservation & Recycling Upcycling Wheat and Barley Straws into Sustainable Thermal Insulation: Assessment and Treatment for Durability,” *Resources, Conservation and Recycling*, vol. 198, pp. 1-10, 2023. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [51] Dumitru Bolcu, Marius Marinel Stanescu, and Cosmin Mihai Mirițoiu, “Some Mechanical Properties of Composite Materials with Chopped Wheat Straw Reinforcer and Hybrid Matrix,” *Polymers*, vol. 14, no. 15, pp. 1-17, 2022. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [52] Razieh Shafiei Alavijeh et al., “Biorefining of Corn Stover for Efficient Production of Bioethanol, Biodiesel, Biomethane, and Value-Added Byproducts,” *Energy Conversion and Management*, vol. 283, 2023. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]

- [53] Cuiping Zhu et al., “Preparation of Cellulose-Based Porous Adsorption Materials Derived from Corn Straw for Wastewater Purification,” *International Journal of Biological Macromolecules*, vol. 233, 2023. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [54] Xueli Zhao et al., “High-Potency White-Rot Fungal Strains and Duration of Fermentation to Optimize Corn Straw as Ruminant Feed,” *Bioresource Technology*, vol. 312, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [55] Stefania Liuzzi et al., “Characterization of Biomass-Based Materials for Building Applications: The Case of Straw and Olive Tree Waste,” *Industrial Crops and Products*, vol. 147, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [56] Daniel Peter Storer et al., “Graphene and Rice-Straw-Fiber-Based 3D Photothermal Aerogels for Highly Efficient Solar Evaporation,” *ACS Applied Materials and Interfaces*, vol. 12, no. 13, pp. 15279-15287, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [57] Weiyi Zhang et al., “Lauric-Stearic Acid Eutectic Mixture/Carbonized Biomass Waste Corn Cob Composite Phase Change Materials: Preparation and Thermal Characterization,” *Thermochimica Acta*, vol. 674, pp. 21-27, 2019. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [58] Angjian Wu et al., “Fabrication of Waste Biomass Derived Carbon by Pyrolysis,” *Materials Letters*, vol. 173, pp. 60-63, 2016. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [59] Cesar Juarez et al., “Performance of “Agave Lecheguilla” Natural Fiber in Portland Cement Composites Exposed to Severe Environment Conditions,” *Building and Environment*, vol. 42, no. 3, pp. 1151-1157, 2007. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [60] Jiewei Tong et al., “Development of Transparent Composites using Wheat Straw Fibers for Light-Transmitting Building Applications,” *Industrial Crops and Products*, vol. 170, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [61] Andrzej K. Bledzki, Abdullah A. Mamun, and Jurgen Volk, “Barley Husk and Coconut Shell Reinforced Polypropylene Composites: The Effect of Fibre Physical, Chemical and Surface Properties,” *Composites Science and Technology*, vol. 70, no. 5, pp. 840-846, 2010. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [62] Jose Antonio Silva-Guzmán et al., “Properties of Thermoplastic Corn Starch Based Green Composites Reinforced with Barley (*Hordeum Vulgare* L) Straw Particles Obtained by Thermal Compression,” *Fibers and Polymers*, vol. 19, pp. 1970-1979, 2018. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [63] M. Bederina et al., “Improvement of the Properties of a Sand Concrete Containing Barley Straws–Treatment of the Barley Straws,” *Construction and Building Materials*, vol. 115, pp. 464-477, 2016. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [64] Ferran Serra-Parareda et al., “Feasibility of Barley Straw Fibers as Reinforcement in Fully Biobased Polyethylene Composites: Macro and Micro Mechanics of the Flexural Strength,” *Molecules*, vol. 25, no. 9, pp. 1-16, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [65] Basheer Aaliya, Kappat Valiyapeediyekkal Sunooja, and Maximilian Lacknerb, “Biopolymer Composites: A Review,” *International Journal of Biobased Plastics*, vol. 3, no. 1, pp. 40-84, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [66] Asanda Mtibe et al., “Synthetic Biopolymers and their Composites: Advantages and Limitations-An Overview,” *Macromolecular Rapid Communications*, vol. 42, no. 15, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [67] P. Manimaran et al., “Extraction and Characterization of Natural Lignocellulosic Fibres from Typha Angustata Grass,” *International Journal of Biological Macromolecules*, vol. 222, pp. 1840-1851, 2022. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [68] Corina L. Reichert et al., “Bio-Based Packaging: Materials, Modifications, Industrial Applications and Sustainability,” *Polymers*, vol. 12, no. 7, pp. 1-35, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [69] G.R. Arpitha et al., “Effect of Sugarcane Bagasse and Alumina Reinforcements on Physical, Mechanical, and Thermal Characteristics of Epoxy Composites using Artificial Neural Networks and Response Surface Methodology,” *Biomass Conversion and Biorefinery*, vol. 14, pp. 12539-12557, 2023. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [70] A. Vinod et al., “Fully Bio-Based Agro-Waste Soy Stem Fiber Reinforced Bio-Epoxy Composites for Lightweight Structural Applications: Influence of Surface Modification Techniques,” *Construction and Building Materials*, vol. 303, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [71] Hanafi Ismail, M.R. Edyham, and B. Wirjosentono, “Bamboo Fibre Filled Natural Rubber Composites: The Effects of Filler Loading and Bonding Agent,” *Polymer Testing*, vol. 21, no. 2, pp. 139-144, 2002. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [72] Thimmapuram Ranjeth Kumar Reddy, Hyun-Joong Kim, and Ji-Won Park, *Renewable Biocomposite Properties and their Applications*, Composites from Renewable and Sustainable Materials, Intechopen, vol. 10, pp. 177-197, 2016. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [73] Raj Kumar Dahal, Bishnu Acharya, and Animesh Dutta, “Mechanical, Thermal, and Acoustic Properties of Hemp and Biocomposite Materials: A Review,” *Journal of Composites Science*, vol. 6, no. 12, pp. 1-21, 2022. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [74] Youssef Cherradi et al., “Acoustic Properties for Composite Materials Based on Alfa and Wood Fibers,” *Applied Acoustics*, vol. 174, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [75] Susan Anenberg et al., “A Global Snapshot of the Air Pollution-Related Health Impacts of Transportation Sector Emissions in 2010 and 2015,” International Council on Clean Transportation, Washington, DC, USA, Report, pp. 1-55, 2019. [[Google Scholar](#)] [[Publisher Link](#)]
- [76] R.V. Hemavathy et al., “Adsorptive Separation of Cu (II) Ions from Aqueous Medium using Thermally/Chemically Treated Cassia Fistula Based Biochar,” *Journal of Cleaner Production*, vol. 249, 2020. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]

- [77] P. Senthil Kumar et al., “Nanoscale Zero-Valent Iron-Impregnated Agricultural Waste as an Effective Biosorbent for the Removal of Heavy Metal Ions from Wastewater,” *Textiles and Clothing Sustainability*, vol. 2, pp. 1-11, 2017. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [78] A. Saravanakumar, S. Sivalingam, and L. Rajesh Kumar, “Dry Sliding Wear of AA2219/Gr Metal Matrix Composites,” *Materials Today: Proceedings*, vol. 5, no. 2, pp. 8321-8327, 2018. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [79] P. Senthil Kumar et al., “Adsorption Isotherms, Kinetics and Mechanism of Pb (II) Ions Removal from Aqueous Solution using Chemically Modified Agricultural Waste,” *The Canadian Journal of Chemical Engineering*, vol. 91, no. 12, pp. 1950-1956, 2013. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [80] Food and Agriculture Organization, *The State of Food and Agriculture 2017: Leveraging Food Systems for Inclusive Rural Transformation*, Food and Agriculture Organization of the United Nations, pp. 1-190, 2017. [[Google Scholar](#)] [[Publisher Link](#)]
- [81] Obed Akampumuza et al., “Review of the Applications of Biocomposites in the Automotive Industry,” *Polymer Composites*, vol. 38, no. 11, pp. 2553-2569, 2017. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [82] Mark Holmes, “Biocomposites Take Natural Step Forward: Applications for Biocomposites and the Use of Natural Fiber Reinforcements are increasing. Reinforced Plastics Looks at a Number of Examples,” *Reinforced Plastics*, vol. 63, no. 4, pp. 194-201, 2019. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [83] Paulo Pecas et al., “Natural Fibre Composites and their Applications: A Review,” *Journal of Composites Science*, vol. 2, no. 4, pp. 1-20, 2018. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [84] R.D.S.G. Campilho, *10 - Recent Innovations in Biocomposite Products*, Biocomposites for High-Performance Applications, Woodhead Publishing, pp. 275-306, 2017. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]
- [85] Mohammad Azad Alam et al., *Chapter 1 Application of Biocomposites in Automotive Components: A Review*, Biocomposite and Synthetic Composites for Automotive Applications, Woodhead Publishing, pp. 1-17, 2021. [[CrossRef](#)] [[Google Scholar](#)] [[Publisher Link](#)]